

Molecular and dissociative absorption of multiple hydrogens on transition metal decorated C_{60}

T. Yildirim,^{1,*} Jorge Íñiguez,² and S. Ciraci³

¹*NIST Center for Neutron Research, National Institute of Standards and Technology, Gaithersburg, MD 20899*

²*Institut de Ciència de Materials de Barcelona (CSIC),
Campus de la UAB, 08193 Bellaterra, Barcelona, Spain*

³*Physics Department, Bilkent University, 06800 Bilkent, Ankara, Turkey*

Recently we have predicted [Phys. Rev. Lett. May 2005] that Ti-decorated carbon nanotubes can absorb up to 8-wt% hydrogen at ambient conditions. Here we show that similar phenomena occurs in light transition-metal decorated C_{60} . While Sc and Ti prefers the hexagon (H) sites with a binding energy of 2.1 eV, V and Cr prefers double-bond (D) sites with binding energies of 1.3 and 0.8 eV, respectively. Heavier metals such as Mn, Fe, and Co do not bond on C_{60} . Once the metals are absorbed on C_{60} , each can bind up to four hydrogen molecules with an average binding energy of 0.3-0.5 eV/ H_2 . At high metal-coverage, we show that a C_{60} can accommodate six D-site and eight H-site metals, which can reversible absorb up to 56 H_2 molecules, corresponding to 7.5 wt%.

PACS numbers: 61.46.+w, 68.43.-h, 84.60.Ve, 81.07.De

An efficient storage media for hydrogen is crucial for the advancement of hydrogen and fuel-cell technologies¹. There have been a great number of reports on the search for new routes to engineer nanomaterials so that (a) they dissociate H_2 molecules into H atoms and (b) reversibly adsorb hydrogen molecules at ambient conditions^{1,2,3,4,5,6,7,8,9}. Much effort has been focused on the engineering of carbon-based materials such as nanotubes^{10,11} and metal hydrides such as alanates¹². It is found that while hydrogen-carbon interaction is too weak¹⁰, the metal-hydrogen interaction is too strong for hydrogen storage at ambient conditions. Very recently we have shown¹³ a novel way to overcome this difficulty by forming artificial metal-carbide like structures on carbon single-wall nanotubes (SWNT). From accurate first-principles calculations, we show that a single Ti-atom adsorbed on a SWNT can strongly bind up to four hydrogen molecules¹³. At large Ti coverage we find that a (8,0) SWNT can store hydrogen molecules up to 8-wt%, exceeding the minimum requirement of 6-wt% for practical applications. Even though these results were totally unexpected, we explained them by a simple Dewar, Chatt, and Duncanson (DCD) model^{14,15}, where the interaction is due to donation of charge from the highest occupied orbital of the ligand to the metal empty states and a subsequent back donation from filled d-orbitals into the lowest unoccupied orbital of the ligand.

Here we show that similar phenomena also occurs in light-transition metal decorated C_{60} molecules. Below we first discuss several possible absorption sites for a single Ti atom on a C_{60} molecule. We then show how a single Ti atom on a C_{60} can bind up to four hydrogen molecules via Kubas interaction^{14,15}. Multiple metal coverage cases, yielding up to 8 wt% hydrogen absorption, are discussed next. Finally, we briefly discuss the results for other transition metals from Sc to Co.

The energy calculations were performed within the plane-wave implementation¹⁶ of the generalized gradient approximation¹⁷ to DFT. We used Vanderbilt ultra-

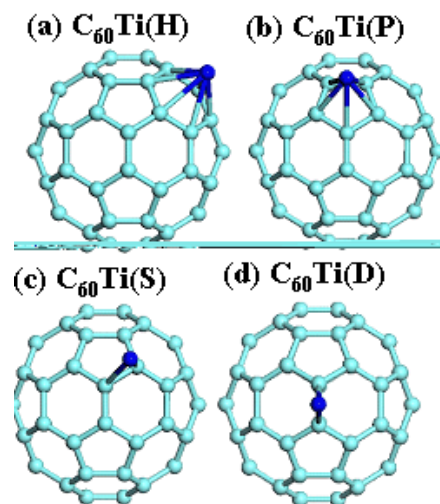


FIG. 1: A single Ti atom absorbed at hexagonal (H) (a) and pentagonal (P) (b) hollow sites, and double (D) and single (S) bond sites of a C_{60} molecule, respectively.

soft pseudopotentials¹⁸ treating the following electronic states as valence: Ti: $3s^2 3p^6 3d^2 4s^2$, C: $2s^2 2p^2$ and H: $1s$. The cutoff energy of 350 eV is found to be enough for total energies to converge within 0.5 meV/atom. The calculations are carried out in a cubic supercell of 16 Å of side for single-metal C_{60} systems and 20 Å for full-coverage cases. We also carried out spin-polarized calculations for cases where the ground state of the metal-coated C_{60} is magnetic. Structural relaxations were considered to be converged when forces on atoms were smaller than 0.2 eV/Å.

Figure 1 shows the four possible absorption sites on a C_{60} molecule that are considered in this study. The C_{60} molecule has the truncated-icosahedral symmetry with twenty hexagons (H), twelve pentagons (P), thirty double C-C bonds (D) between two hexagons and sixty single

	C ₆₀ Ti(H)	C ₆₀ Ti(P)	C ₆₀ Ti(D)	C ₆₀ Ti(S)
d(Ti-C) (Å)	2.27	2.33	2.10	2.24
d(C-C) (Å)	1.42/1.45	1.44	1.52	1.48
Q(Ti) (e)	1.39	1.09	0.99	0.84
S(Ti)	0.99 $\hbar$	1.40 $\hbar$	1.13 $\hbar$	1.54 $\hbar$
E _B (Ti) (eV)	2.098	1.633	1.837	1.220

TABLE I: The calculated Ti-C and C-C bond distances, the Mulliken charges, spins and the binding energies for a single Ti atom absorbed at four different sites of a C₆₀ molecule as shown in Fig.1. For bare C₆₀ the calculated double and single bond lengths are 1.44 Å and 1.38 Å, respectively.

C-C bonds (S) which are between pentagon and hexagon carbon rings. We calculated the binding energy of a single Ti atom at these sites, which are listed in Table I along with relevant structural parameters. The binding energy is defined as

$$E_B(Ti) = E(C_{60}) + E_{spol}(Ti) - E_{spol}(C_{60}Ti), \quad (1)$$

where E_{spol} is the spin-polarized energy. Hence the positive binding energy indicates the stability of the system.

The results in Table I indicate that H-site is the most stable configuration for C₆₀Ti with a binding energy of 2.1 eV. The D-site comes next with the shortest Ti-C bonds among the four possible configurations. For all cases, we have about one electron charge transfer to the C₆₀ molecule. The S-site is the least stable absorption site and therefore we do not consider it any further.

Figure 2(a) shows the energy variation from *spin-unpolarized* calculations as a single H₂ molecule approaches C₆₀Ti(D). The energy first decreases slowly as the hydrogen gets closer to the C₆₀ and Ti. However, as the charge overlap gets large, the H₂ molecule is attracted towards the Ti atom with a sudden decrease in the energy. At this point, the H₂ molecule is still intact with a significantly increased H-H bond length of 0.9 Å. The second sudden decrease in energy is achieved by dissociating the H₂ molecule into two H atoms. At this point, the H-H distance increases from 0.9 Å to 2.94 Å. The interaction between H₂ and C₆₀Ti(D) is always attractive and therefore H₂ is absorbed onto a Ti atom without any energy barrier. The final geometry is shown in the inset to Fig. 2(a), with relevant structural parameters given¹⁹. In order to calculate the binding energy for this dissociative adsorption, we calculate total energies of the initial C₆₀Ti(D) and H₂ states and the final C₆₀Ti(D)H₂ state (dashed lines in Fig. 1(a)) from spin-polarized calculations. We obtained the binding energy to be 1.16 eV (Fig. 2(a)).

Figure 2(b) shows the energy variation as two hydrogen molecules approach the Ti atom; one from each side of the TiH₂ group. As in the case of single adsorption, the energy always decreases, first slowly and later very rapidly at which point both hydrogen molecules are strongly attached to the C₆₀Ti(D)H₂ system. In the final

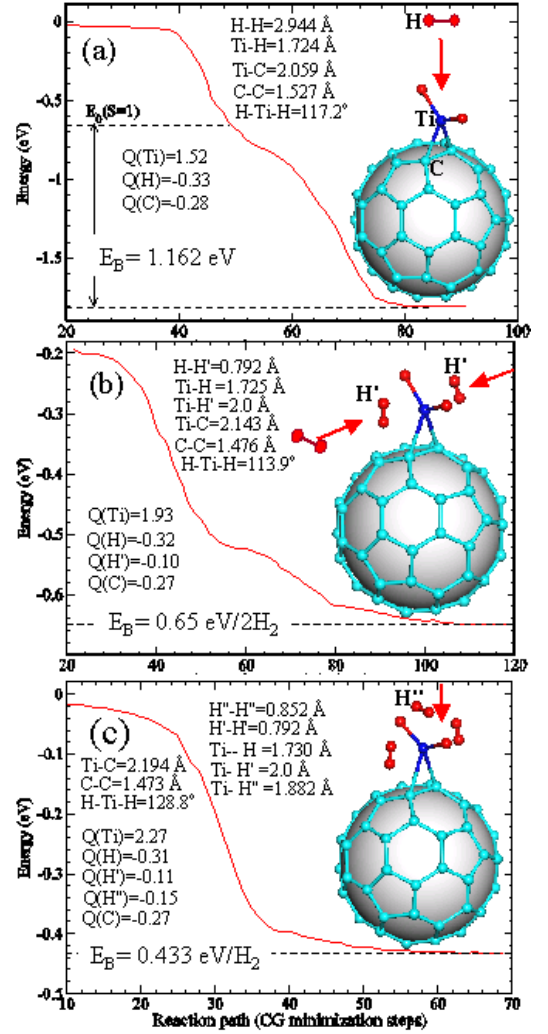


FIG. 2: Energy versus reaction paths for successive dissociative and molecular adsorption of H₂ over a single C₆₀Ti(D). (a) H₂ + C₆₀Ti(D) → C₆₀Ti(D)H₂. (b) 2H₂ + C₆₀Ti(D)H₂ → C₆₀Ti(D)H₂-2H₂. (c) H₂ + C₆₀Ti(D)H₂-2H₂ → C₆₀Ti(D)H₂-3H₂. The zero of energy is taken as the sum of the energies of two reactants.

configuration, we note that two H₂ molecules were rotated by 90° as shown in Fig. 2(b). We denote the final product as C₆₀Ti(D)H₂-2H₂. The total energy change upon adsorption is about 0.65 eV (i.e. 0.325 eV/H₂). Unlike the first adsorption, the two hydrogen molecules are in intact but with a rather elongated bond length of 0.79 Å.

Figure 2(c) shows the energy evolution when a fourth hydrogen molecule approaches the C₆₀Ti(D)H₂-2H₂ system from the top. The energy again decreases continuously, indicating a zero-energy barrier. The final product, denoted as C₆₀Ti(D)H₂-3H₂, is shown in the inset with the relevant structural parameters. The energy gained by the fourth adsorption, 0.433 eV/H₂, is slightly larger than for the previous one. The H-H distance of the top H₂ is 0.85 Å. Several attempts to add a fifth hydrogen

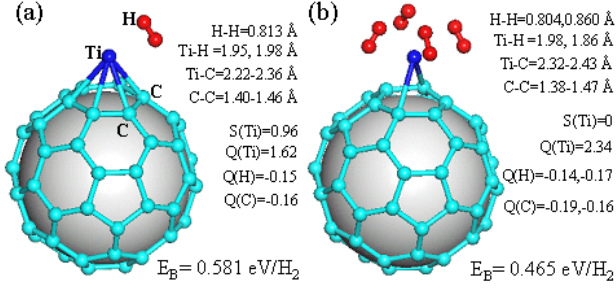


FIG. 3: Molecular absorption of a single (a) and four H₂ on C₆₀Ti(H). The binding energies and relevant structural parameters are also given.

molecule at a variety of positions failed, suggesting a limit of 4 H₂/Ti. However in the view of a recent study²⁰ which shows that it is possible to attach twelve hydrogen atoms to a single transition metal, it is quite possible that there may be other transition paths that could yield more than four hydrogen molecules per C₆₀Ti.

We next discuss the hydrogen absorption properties of a Ti on the H-site of a C₆₀ as shown in Fig. 3. For the first hydrogen absorption, we find that the H₂ stay intact unlike the case of Ti on a D-site where the first H₂ is absorbed dissociatively as shown in Fig. 2(a). This is due the fact that Ti is absorbed on H-site very strongly and therefore there is not enough charge left on Ti to transfer to the σ^* of H₂ to dissociate it¹³. The binding energy is about 0.58 eV and H-H bond length is 0.813 Å. Introducing additional hydrogen molecules yield more molecular absorption without any energy barrier up to 4H₂/Ti, which is denoted as C₆₀Ti(H)-4H₂ and shown in Fig. 3(b). The final optimized structure is very symmetric, all hydrogen molecules benefit equally from the bonding with Ti atom. The average binding energy per H₂ is about 0.465 eV, slightly smaller than the one of the first absorption. We have also calculated the binding energy for the isomer, C₆₀Ti(H)H₂-3H₂, where the first H₂ is bonded to Ti dissociatively. We find that this isomer is about 0.1 eV higher in energy than C₆₀Ti(H)-4H₂.

The results for the absorption of hydrogens on the P-site Ti are summarized in Fig. 4. The first absorption is found to be dissociative without activation energy. The binding energy is about 0.615 eV, significantly smaller than that of Ti on D-site (see Fig. 2(a)), but the absorption is still dissociative unlike Ti on H-site (see Fig. 3(a)). The two isomers, C₆₀Ti(P)H₂-3H₂ (Fig. 4(b)) and C₆₀Ti(P)-4H₂ (Fig. 4(c)), are found to be almost degenerate and yield a binding energy of 0.43 eV/H₂.

To this point we have discussed the interaction of H₂ with a single Ti atom bonded to a C₆₀, but clearly one can imagine attaching more Ti to a C₆₀, thereby increasing the hydrogen storage capacity. In order to show the feasibility of this approach, we consider several cases. Fig. 4(d) shows the full coverage case where all the P-sites of a C₆₀ molecule is absorbed by Ti atoms, each of which binds four H₂ molecules. The calculated aver-

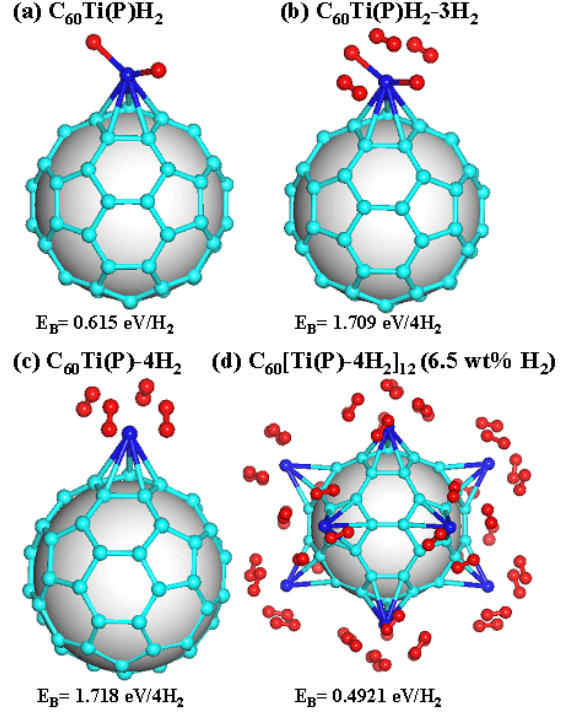


FIG. 4: The optimized structure of one (a) and two isomers (b-c) of four hydrogen molecules absorbed on a single Ti atom on P-site of a C₆₀. (d) Full coverage case where all twelve pentagon sites are decorated by Ti, each of which absorbs four H₂ molecules.

age binding energy for each hydrogen molecule is 0.492 eV/H₂. This is slightly higher than the single-coverage case as shown in Fig. 4(c). This is due to the more symmetric configuration of the full coverage case, where C₆₀ does not have to distort locally as in single-coverage case. In fact, we see the same effect in the binding energy of Ti atom on P-site, which is 1.633 eV (see Table I), for a single Ti atom. However it becomes 2.115 eV/Ti when all the P-sites are absorbed by Ti. These results are quite promising, suggesting that the full coverage system is more stable than the single-atom coverage.

Figure 5(a) shows another case where six Ti atoms absorbed on the D-sites (those sites along the two-fold axis of the C₆₀ molecule). As in the case of full pentagonal-coverage, the average binding energy per H₂ is slightly increased to 0.592 eV from the single Ti value of 0.559 eV. Interestingly, one can further add eight more Ti-atoms at the hexagonal faces of the C₆₀ molecules (those along the [111] directions), yielding total 14 Ti atoms per C₆₀. The full hydrogen absorbed case of this coverage is shown in Fig. 5(b). The average binding energy is 0.522 eV/H₂, in excellent agreement with the 0.505 eV/H₂ based on the single Ti-atom cases. This indicates that the 14 Ti atoms and 56 hydrogen molecules shown in Fig. 4(b) are not too close to each other and therefore suggest that the system has the capacity to have many Ti and hydrogen. In fact, the configuration shown in Fig. 5(b), which have

Properties	C ₆₀ Sc(H)	C ₆₀ Ti(H)	C ₆₀ V(D)	C ₆₀ Cr(D)	C ₆₀ Mn(D)	C ₆₀ Fe(D)	C ₆₀ Co(D)
d(TM-C) (Å)	2.29	2.27	2.18	2.09	2.30	2.28	2.26
d(C-C) (Å)	1.42/1.46	1.42/1.45	1.46	1.50	1.45	1.45	1.45
Q(TM) (e)	1.55	1.39	0.78	0.91	0.97	0.86	0.76
S(TM)	0.24 $\hbar$	0.99 $\hbar$	2.0 $\hbar$	2.35 $\hbar$	2.99 $\hbar$	2.53 $\hbar$	1.54 $\hbar$
E _B (TM) (eV)	2.127	2.098	1.308	0.760	-0.017	-0.130	-0.503
E _B (H ₂) (eV)	0.300	0.454	0.497	0.239	-0.092	-	-

TABLE II: The calculated TM-C and C-C bond distances, the Mulliken charges, spins and the binding energies for a single TM atom (TM=Sc, Ti, V, etc) absorbed on a C₆₀ molecule.

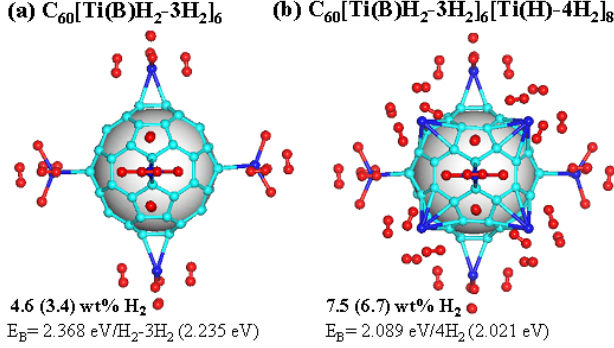


FIG. 5: Two high-density coverage on Ti-coated C₆₀, corresponding to 4.3 wt% and 7.5 wt% hydrogen storage when all hydrogens can be released and 3.4 wt% and 6.7% storage when only molecularly absorbed hydrogens are released.

the chemical formula, C₆₀Ti₁₄H₅₆, stores approximately 7.5-wt% hydrogen.

It is important to know if the results reported above for the C₆₀Ti system hold for other transition metals. Therefore we have also studied the transition metals from Sc to Co. Table II summarizes our results for the binding energies and relevant structural parameters. Briefly we find that while Sc and Ti prefers the H-site, V and Cr prefers the D-sites. The binding energies monotonically decreases as we move from left to the right of the periodic table. In fact for heavy transition metals such as Mn, Fe, and Co, we obtained negative binding energy,

indicating that the system is not stable against C₆₀ and isolated metal atom formation. We also confirmed that similar hydrogen absorption happens for the other transition metals. The last line in Table II indicates the average binding energy per H₂ in C₆₀TMH₂-3H₂ configurations where TM=Sc, V, etc. It increases from 0.3 eV/H₂ for Sc to 0.5 eV/H₂ for V and then decreases to 0.239 eV/H₂ for Cr and then the system becomes unstable for heavier transition metals.

In conclusion, using the state-of-the-art first-principles calculations we show that light-transition metal-decorated C₆₀ molecules exhibit remarkable hydrogen storage properties. Metals bonded on the D-site dissociate the first H₂ molecule without any activation barrier and then reversible and molecularly bond three more hydrogens. However metals absorbed at the H-sites binds four hydrogen molecules without dissociating it. Combining these two binding sites we shows that a single C₆₀ molecule is able to bind up to 56 H₂ molecules, corresponding to 7.5 wt% storage capacity. These results combined with our previous work in Ti-decorated SWNT¹³ suggest a new direction to high-capacity hydrogen storage materials by decorating light-transition metals on nanostructured materials. The nature of hydrogen bonding is explained by DCD model^{14,15} and has the right strength for room temperature reversible hydrogen storage.

This work was partially supported by DOE under Grant No. DEFC36-04-GO14280.

* Electronic address: taner@nist.gov

¹ For a review see the special issue *Towards a Hydrogen Economy* in Science **305**, 958 (2004).

² S. P. Chan, G. Chen, X. G. Gong, Z. F. Liu, Phys. Rev. Lett. **87**, 205502 (2001).

³ K. Tada, S. Furuya, and K. Watanabe, Phys. Rev. B **63**, 155405 (2001).

⁴ Y. Miura *et al.*, J. App. Phys. **93**, 3395 (2003).

⁵ G. Lu, H. Scudder, and N. Kioussis, Phys. Rev. B **68**, 205416 (2003).

⁶ P. Dubot and P. Cenedese, Phys. Rev. B **63**, 241402 (R) (2001).

⁷ E. C. Lee, Y.-S. Kim, Y.-G. Jin, and K. J. Chang, Phys. Rev. B **66**, 073415 (2002).

⁸ O. Gulseren, T. Yildirim, S. Ciraci, Phys. Rev. B **66**, 121401 (R) (2002).

⁹ O. Gulseren, T. Yildirim, S. Ciraci, Phys. Rev. Lett. **87**, 116802 (2001).

¹⁰ S. Dag, Y. Ozturk, S. Ciraci, and T. Yildirim, Phys. Rev. B (submitted, 2005) (see also cond-mat/0504696).

¹¹ W. Q. Deng, X. Xu, and W. A. Goddard, Phys. Rev. Lett. **92**, 166103 (2004).

¹² B. Bogdanovic, M. Felderhoff, S. Kaskel, A. Pommerin, K. Schlichte, and F. Schuth, Adv. Mater. **15**, 1012 (2003).

- ¹³ T. Yildirim and S. Ciraci, Phys. Rev. Lett., May Issue, 2005 (see also cond-mat/0504694) .
- ¹⁴ *Metal Dihydrogen and Bond Complexes- Structure, Theory, and Reactivity*, G. J. Kubas (Kluwer Academic/Plenum Pub., 2001).
- ¹⁵ J. Chatt and L. Duncanson, J. Chem. Soc. 2939 (1953).
- ¹⁶ M. C. Payne *et. al.*, Rev. Mod. Phys. **64**, 1045 (1992).
- ¹⁷ P. J. Perdew, K. Burke, M. Ernzerhof, Phys. Rev. Lett. **77**, 3865 (1996).
- ¹⁸ D. Vanderbilt, Phys. Rev. B **41**, 7892 (1990).
- ¹⁹ The animations of the reaction paths and MD simulations can be found at <http://www.ncnr.nist.gov/staff/taner/h2>
- ²⁰ L. Gagliardi and P. Pyrkko, J. Am. Chem. Soc. **126**, 15014 (2004).